

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

SPONSOR: **Moxie Surfaces**
Encinitas, CA

Sound Absorption
RAL™-A24-155

CONDUCTED: 2024-03-20

Page 1 of 10

ON: AIR-board Acoustic Quiet – 1” (Type F-100 Mounting)

TEST METHODOLOGY

Riverbank Acoustical Laboratories™ is accredited by the U.S. Department of Commerce, National Institute of Standards and Technology (NIST) under the National Voluntary Laboratory Accreditation Program (NVLAP) as an ISO 17025:2017 Laboratory (NVLAP Lab Code: 100227-0) and for this test procedure. The test reported in this document conformed explicitly with ASTM C423-23: "Standard Test Method for Sound Absorption and Sound Absorption Coefficients by the Reverberation Room Method." The specimen mounting was performed according to ASTM E795-23: "Standard Practices for Mounting Test Specimens During Sound Absorption Tests." A description of the measurement procedure and room specifications are available upon request. The results presented in this report apply to the sample as received from the test sponsor.

INFORMATION PROVIDED BY SPONSOR

The test specimen was designated by the sponsor as AIR-board Acoustic Quiet – 1”. The following nominal product information was provided by the sponsor prior to testing. The accuracy of such sponsor-provided information can affect the validity of the test results.

Product Under Test

Product Name: AIR-board Acoustic Quiet – 1”
Manufacturer: Design Composite
US Distributor: Moxie Surfaces

SPECIMEN MEASUREMENTS & TEST CONDITIONS

Through a full external visual inspection performed on the test specimen, Riverbank personnel verified the following information:

Test Specimen

Material: Panels with honeycomb core, microperforated sheet on one side, solid sheet on other side
Dimensions: 2 panels @ 1219 mm (48 in.) by 2438 mm (96 in.)
Thickness: 26.35 mm (1.0375 in.)
Overall Weight: 31.52 kg (69.5 lbs)

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

Moxie Surfaces
2024-03-20

RAL™-A24-155
Page 2 of 10

Overall Specimen Properties

Size: 2.44 m (96.0 in) wide by 2.44 m (96.0 in) long
Thickness: 0.03 m (1.0375 in)
Weight: 31.52 kg (69.5 lbs)
Mass per Unit Area: 5.3 kg/m² (1.09 lbs/ft²)
Calculation Area: 5.946 m² (64. ft²)

Test Environment

Room Volume: 291.98 m³
Temperature: 21.3 °C ± 0.2 °C (Requirement: ≥ 10 °C and ≤ 5 °C change)
Relative Humidity: 59.55 % ± 2.9 % (Requirement: ≥ 40 % and ≤ 5 % change)
Barometric Pressure: 99.0 kPa (Requirement not defined)

MOUNTING METHOD

Type F-100 Mounting: The test specimen was laid over wood spacers placed on the horizontal test surface, creating a 102 mm (4 in.) thick airspace between the test surface and the panel body. The numeral suffix in the mounting designation is the thickness of the spacers in millimeters, rounded to the nearest integer multiple of 5. Perimeter edges were sealed with wood and metal framing and tape.

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

Moxie Surfaces
2024-03-20

RAL™-A24-155

Page 3 of 10



Figure 1 – Specimen mounted in test chamber



Figure 2 – Individual specimen panel

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

Moxie Surfaces
2024-03-20

RAL™-A24-155

Page 4 of 10



Figure 3 – Wood spacers in test chamber



Figure 4 – Specimen partially installed over spacers

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

Moxie Surfaces
2024-03-20

RAL™-A24-155
Page 5 of 10



Figure 5 – Detail of specimen materials

627 RIVERBANK DRIVE
 GENEVA, IL 60134
 630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
 WALLACE CLEMENT SABINE

Moxie Surfaces
 2024-03-20

RAL™-A24-155
 Page 6 of 10

TEST RESULTS

Specimen total absorption and absorption coefficient are tabulated at the eighteen standard frequencies. A graphic presentation of the data and additional information appear on the following pages.

1/3 Octave Center Frequency (Hz)	Total Absorption (m ²)	Total Absorption (Sabins)	Absorption Coefficient
100	4.28	46.10	0.72
** 125	3.05	32.84	0.51
160	1.82	19.59	0.31
200	1.72	18.48	0.29
** 250	1.44	15.52	0.24
315	1.19	12.76	0.20
400	1.08	11.65	0.18
** 500	1.13	12.18	0.19
630	1.42	15.28	0.24
800	1.80	19.35	0.30
** 1000	2.43	26.18	0.41
1250	2.84	30.61	0.48
1600	3.04	32.69	0.51
** 2000	3.11	33.47	0.52
2500	2.86	30.82	0.48
3150	2.50	26.95	0.42
** 4000	1.77	19.09	0.30
5000	1.18	12.65	0.20

SAA = 0.34
NRC = 0.35

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE


Moxie Surfaces
2024-03-20

RAL™-A24-155
Page 7 of 10


TEST RESULTS (continued)

The sound absorption average (SAA) is defined in ASTM C423-23 Section 3.1.1 as the arithmetic average of the sound absorption coefficients of a material for the twelve one-third octave bands from 200 Hz through 2500 Hz, inclusive, rounded to the nearest integer multiple of 0.01.

The noise reduction coefficient (NRC) is defined from previous versions of ASTM C423 as the arithmetic average of the sound absorption coefficients at 250 Hz, 500 Hz, 1000 Hz, and 2000 Hz, rounded to the nearest integer multiple of 0.05.

Tested by 
Marc Sciaky
Senior Experimentalist

Report by 
Keith Kimberling
Test Engineer

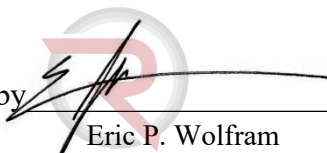Approved by 
Eric P. Wolfram
Laboratory Manager

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report


www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

Moxie Surfaces
2024-03-20

RAL™-A24-155
Page 8 of 10

SOUND ABSORPTION REPORT
AIR-board Acoustic Quiet – 1”

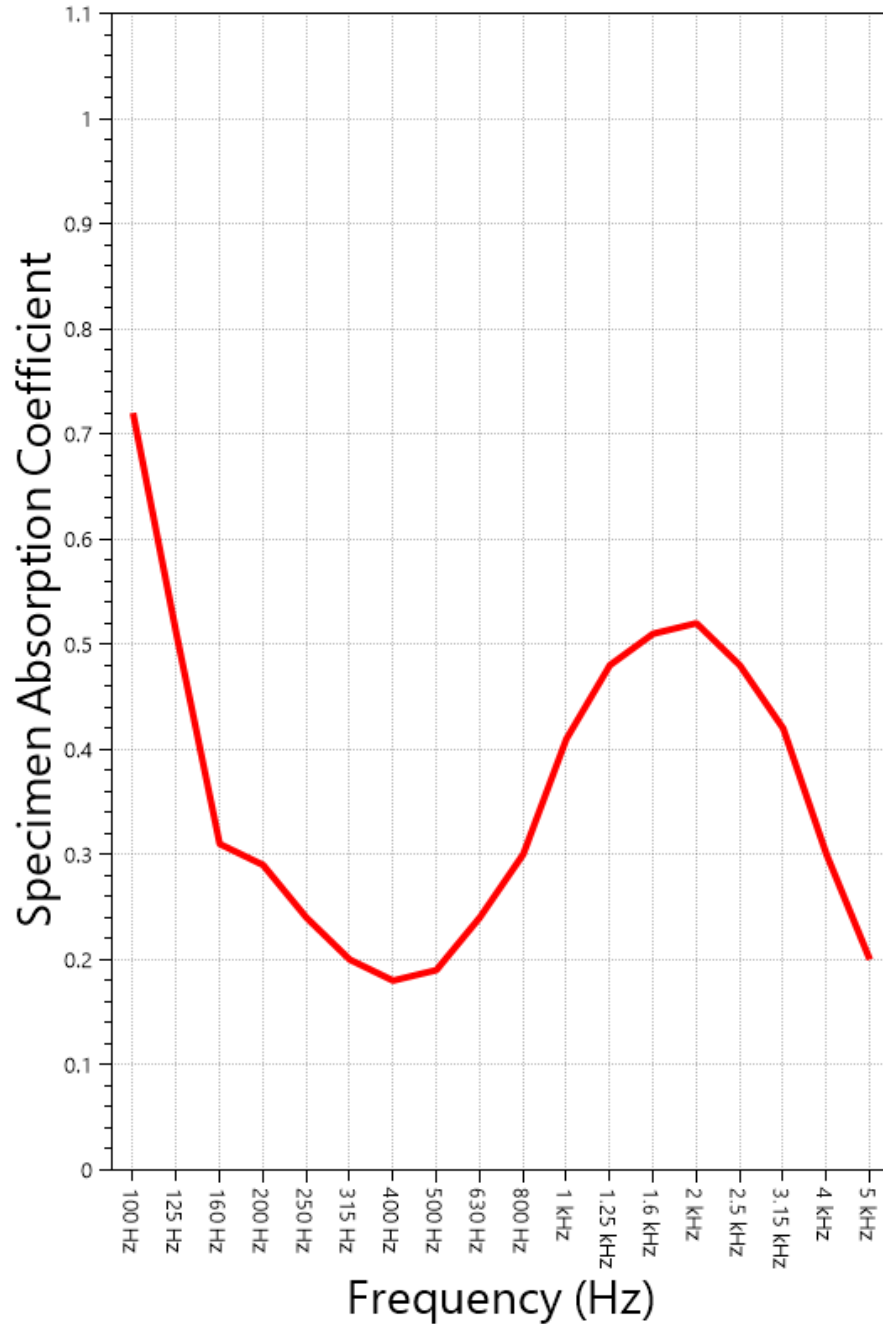

SAA = 0.34
NRC = 0.35



RIVERBANK ACOUSTICAL LABORATORIES IS ACCREDITED BY NVLAP (LAB CODE 100227-0) FOR ACOUSTICAL TESTING SERVICES IN ACCORDANCE WITH ISO/IEC 17025:2017 AND FOR THIS PROCEDURE. THIS REPORT MUST NOT BE USED BY THE CLIENT TO CLAIM PRODUCT CERTIFICATION, APPROVAL, OR ENDORSEMENT BY RAL, NVLAP, NIST, OR ANY AGENCY OF THE U.S. GOVERNMENT. THIS REPORT SHALL NOT BE MODIFIED WITHOUT THE WRITTEN APPROVAL OF RAL. THE RESULTS REPORTED APPLY ONLY TO THE SPECIFIC SAMPLE SUBMITTED FOR TESTING; RAL ASSUMES NO RESPONSIBILITY FOR THE PERFORMANCE OF ANY OTHER SAMPLE.

627 RIVERBANK DRIVE
 GENEVA, IL 60134
 630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
 WALLACE CLEMENT SABINE

Moxie Surfaces
 2024-03-20

RAL™-A24-155
 Page 9 of 10

APPENDIX A: Extended Frequency Range Data

Specimen: AIR-board Acoustic Quiet – 1” (See Full Report)

The following non-accredited data were obtained in accordance with ASTM C423-23, but extend beyond the defined frequency range of 100Hz to 5,000Hz. These unofficial results are representative of the RAL test environment only and intended for research & comparison purposes.

1/3 Octave Band Center Frequency (Hz)	Total Absorption (Sabins)	Absorption Coefficient
31.5	6.01	0.09
40	1.89	0.03
50	2.83	0.04
63	5.95	0.09
80	23.53	0.37
100	46.10	0.72
125	32.84	0.51
160	19.59	0.31
200	18.48	0.29
250	15.52	0.24
315	12.76	0.20
400	11.65	0.18
500	12.18	0.19
630	15.28	0.24
800	19.35	0.30
1000	26.18	0.41
1250	30.61	0.48
1600	32.69	0.51
2000	33.47	0.52
2500	30.82	0.48
3150	26.95	0.42
4000	19.09	0.30
5000	12.65	0.20
6300	7.17	0.11
8000	21.60	0.34
10000	17.12	0.27
12500	-5.14	-0.08

627 RIVERBANK DRIVE
GENEVA, IL 60134
630-232-0104

Test Report

www.riverbankacoustics.com

FOUNDED 1918 BY
WALLACE CLEMENT SABINE

Moxie Surfaces
2024-03-20

RAL™-A24-155
Page 10 of 10

APPENDIX B: Instruments of Traceability

Specimen: AIR-board Acoustic Quiet – 1” (See Full Report)

<u>Description</u>	<u>Model</u>	<u>Serial Number</u>	<u>Date of Certification</u>	<u>Calibration Due</u>
System 1	Type 3160-A-042	3160-106968	2023-07-17	2024-07-17
Bruel & Kjaer Mic And Preamp G	Type 4943-B-001	2525858	2023-05-03	2024-05-03
Bruel & Kjaer Pistonphone	Type 4228	2781248	2023-07-12	2024-07-12
EXTECH Hygro 6015	SD700	A.116015	2023-05-31	2024-05-31

APPENDIX C: Revisions to Original Test Report

Specimen: AIR-board Acoustic Quiet – 1” (See Full Report)

<u>Date</u>	<u>Revision</u>
2024-04-08	Original report issued

END